

Journal of Materials Chemistry B

Materials for biology and medicine

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: G. Simoncini, F. Marangi, I. Venturino, V. Vurro, A. Bartolucci, L. Vannozzi, L. Aloisio, M. Rossi, P. Moretti, C. Bertarelli, G. M. Paternò and G. Lanzani, *J. Mater. Chem. B*, 2026, DOI: 10.1039/D5TB02640G.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Electrospun Polymeric Scaffold Enables 3D Tissue-like Functionality and Efficient Photoinduced Contraction

Giulia Simoncini^{a,b}, Fabio Marangi^b, Ilaria Venturino^{a,b}, Vito Vurro^b, Andrea Bartolucci^{c,d}, Lorenzo Vannozzi^{c,d}, Ludovico Aloisio^b, Martina Rossi^e, Paola Moretti^e, Chiara Bertarelli^e, Giuseppe Maria Paternò^{a,b*}, Guglielmo Lanzani^{a,b*}

^a Dipartimento di Fisica, Politecnico di Milano, 20133 Milano, Italy

^b Center for Nano Science and Technology, Istituto Italiano di Tecnologia, 20134 Milano, Italy

^c The BioRobotics Institute, Scuola Superiore Sant'Anna, 56025 Pisa, Italy

^d Department of Excellence in Robotics and AI, Scuola Superiore Sant'Anna, 56127 Pisa, Italy

^e Dipartimento di Chimica, Materiali e Ingegneria Chimica "Giulio Natta" Politecnico di Milano, 20133 Milano, Italy

Abstract

Muscle tissue engineering aims to develop functional muscle constructs with controllable contraction for applications in regenerative medicine and drug screening. In this study, we present the development of a biocompatible, light-responsive bio-hybrid construct, combining the electrospinning technique for scaffold fabrication with a phototransducer. The scaffold, composed of electrospun poly(vinyl alcohol) or poly(caprolactone) nanofibers, supports C2C12 myoblast adhesion and alignment, enabling the formation of organized cellular assemblies capable of generating measurable contractions. Light responsiveness is conferred by Ziapin2, a membrane-targeting azobenzene that enables non-genetic, optocapacitive stimulation under visible light exposure.

We fabricated both 2D and self-standing quasi- 3D scaffolds and systematically evaluated their mechanical properties and functional performance, observing that aligned fibers enhanced cellular organization and promoted macroscopic contractions in response to exogenous stimulation. After identifying PVA as the optimal material for quasi- 3D scaffold fabrication, we evaluated the light-induced contractions, which generated strain and stresses of up to 4×10^{-4} and 3.3 kPa, respectively, leading to a contraction force of 460 μ N. These results highlight the potential of aligned, and photosensitized nanofiber scaffolds as biocompatible, optically controllable platforms for engineered muscle tissues, with applications in soft robotics, *in vitro* modeling, drug screening and regenerative medicine.

New Concepts

This work introduces a novel bio-hybrid muscle construct that couples aligned electrospun nanofiber scaffolds with a membrane-targeting phototransducer to achieve light-controlled contractions without genetic manipulation. By integrating fiber alignment with photo-responsiveness, we demonstrate self-standing quasi-3D muscle constructs capable of generating macroscopic contraction forces in response to optical stimuli. This concept links nanofabrication, photochemistry, and tissue engineering, offering a non-invasive, tunable, and scalable platform for bio-actuation. This strategy opens to a different approach for the design of controllable muscle-mimetic systems with potential applications in soft robotics, regenerative medicine, and drug screening.



44 Introduction

View Article Online
DOI: 10.1039/D5TB02640G

45 Tissue engineering aims to develop functional tissues for applications in regenerative medicine,
46 disease modelling, and drug testing. A central challenge in this field is the design of biomimetic
47 scaffolds that provide appropriate structural guidance and mechanical support while enabling
48 externally controlled actuation. In skeletal muscle systems, anisotropic organization and coordinated
49 contraction are essential features that must be recapitulated to achieve tissue-like functionality.^{1–3}
50 Engineering muscle cells into functional tissues has recently gained significant attention, for healing
51 injuries to the motor system and the neuromuscular apparatus, including cardiac muscle.^{4–6} Muscle
52 cells can be seeded onto various substrates or matrices, including hydrogels, elastomers and
53 extracellular matrices, and their contractile motion can be harnessed for diverse functions, such as
54 artificial muscles, pumping, sensing and locomotion.⁶ Numerous studies have explored the
55 cultivation of myoblasts in biocompatible matrices that replicate the stiffness, elasticity, and
56 morphology of natural tissues. 3D-printed gels have been utilized as tridimensional scaffolds for the
57 proliferation and stimulation of cardiomyocytes with external photovoltaic micro-devices.⁷ However,
58 the inherent localized stimulation represents a limitation in the effectiveness of this approach, while
59 an extended stimulation can be provided by molecules dissolved in cells culture medium. Moreover,
60 despite mimicking mechanical properties of living tissue, such system does not provide a preferential
61 alignment to the tissue, which has been demonstrated to be ideal for skeletal muscle cells
62 differentiation and functionality.^{8,9}

63 In particular, electrospun (ES) scaffolds are commonly utilized due to their structural resemblance to
64 the native extracellular matrix (ECM).^{10,11} The nanofibrous scaffolds obtained by electrospinning
65 have morphological, mechanical and biochemical properties that promote cell adhesion and
66 proliferation. Those are essential for myoblast fusion and myotube formation¹². Importantly, when
67 the ES network is deposited along a preferential axis, it can promote cells' alignment. Furthermore,
68 electrospinning enables the easy and versatile fabrication of nanofibrous sheets, which serve as
69 biocompatible scaffolds that support and promote tissue-like cell organization.¹³ All these factors are
70 known to contribute to the formation of aligned and functionally organized muscle tissues.

71 Once cells are grown and organized within the scaffold, their functionality depends on the availability
72 of tools for exogenous contraction stimulation, with minimal side effects and invasiveness. To this
73 end, photostimulation has recently gained attention as a method for regulating cellular activity with
74 relatively high spatial and temporal resolution, selectivity, and less invasiveness compared to
75 electrical stimulation, which remains however the most commonly used technique.¹⁴ Several
76 approaches have been developed to induce light sensitivity in cells^{15–17}, including optogenetics,^{18,19}
77 as well as the use of organic^{20,21} or inorganic semiconductor interfaces.¹⁷ Optogenetics methods
78 have demonstrated strong efficacy in initiating action potentials in activatable cells, and have been
79 successfully adapted for the light-controlled activation of cardiomyocytes and skeletal muscle.^{18,23}

80 Instead, our approach relies on a materials-driven strategy: a membrane-targeting azobenzene
81 molecule capable of triggering contraction in skeletal muscle cells upon light stimulation. Engineered
82 muscle tissues with light-responsive properties could be utilized for regenerative therapies,
83 particularly in cases of muscle degeneration or injury.²⁵ Additionally, these systems hold potential for
84 high-throughput drug screening platforms, where controlled muscle contractions could serve as
85 functional readouts.²⁶ Furthermore, in biohybrid robotics, engineered muscle actuators controlled by
86 light could enable the development of soft, adaptive bio-machines.²⁷ Such an approach benefits from
87 the fact that the mechanical properties of soft actuators more closely resemble those of biological
88 tissues than those of rigid actuators, making them well suited for mimicking the functions of biological
89 appendages, organs and tissues.⁶

90 Here we present biocompatible, ES scaffolds that supports viability, alignment, and light-triggered
91 contractions of organized C2C12 cellular assemblies. The scaffolds are fabricated by electrospinning



poly(vinyl alcohol) (PVA) or poly(caprolactone) (PCL)^{28,29} fibers and loaded with C2C12 cells. PCL and PVA were chosen as well-characterized, biocompatible, and biodegradable polymers, previously used for cells culture and in muscle cell studies.^{30–32} After the myotubes formation, light-sensitivity is conferred by adding a membrane-targeting molecular phototransducer, namely Ziapin2,^{24,33} which induces cell excitation via an optocapacitive effect both *in vitro* and *in vivo*.^{34–36} First, we assessed the functionality of 2D and quasi- 3D networks with the final goal to create a tissue-like, free-standing muscle construct. PVA self-standing membranes were selected for optostimulation experiments in a quasi-3D configuration, as they combine a Young's modulus within the same order of magnitude as contracting skeletal muscle (~ 1 MPa)³⁷ with a high degree of alignment that supports robust myotube formation. Contractile responses of C2C12 under repeated visible-light stimulation were measured, revealing a stress of 3.3 kPa and a strain of 4×10^{-4} , accompanied by linear displacements of $\Delta L \approx 4 \mu\text{m}$ and generated forces of approximately 460 μN . Such values highlight the importance of the need for a three-dimensional cellular organization to activate synergic contractile behaviour. Additionally, by using electrospinning as a technique for developing contractile quasi-3D actuators, we achieve contractile stress values within the range reported for C2C12 3D constructs (1–50 kPa).^{36,38} Intriguingly, photoinduced contractions are within the same order of magnitude of conventional electroinduced pacing, while offering the significant advantage of being far less invasive. By combining anisotropic scaffold architecture with photoresponsive membrane modulation, we establish a biohybrid platform capable of generating measurable contractile forces under optical stimulation. This approach links nanofabrication, soft-matter mechanics, and non-genetic photostimulation to create light-controlled, muscle-like constructs with potential relevance for soft bioactuation, *in vitro* modelling, drug screening, and regenerative medicine.

Experimental

Polycaprolactone solution preparation and electrospinning. The solution was prepared by dissolving PCL (Mw 80,000 Da) at a concentration of 12% w/v in a solvent mixture of chloroform and dimethylformamide (4:1 v/v) and stirred overnight at room temperature.

The solution was ES with an E-Fiber EF100 Electrospinning from Leonardo, through a 20 Gauge (G) needle into randomly oriented and aligned nanofibers using different types of collectors. For both the 2D random and aligned configuration, to avoid fibers detachment from the substrate, the deposition was carried out on microscope glass slides (1cm x 1cm) with a spin coated layer of PCL. The randomly aligned fibers were collected on a flat collector. The deposition process for 2D samples was carried out until a homogeneous layer of fibers formed on the substrate. The electrospinning parameters for random fibers were as follows: flow rate = 4 mL/h, distance from the collector = 15 cm, voltage = 20 kV, temperature = 21°C, and humidity = 50%.

Aligned fibers were obtained using a rotating drum with the same solution concentration and the following parameters: flow rate = 1 mL/h, voltage = 30 kV, distance from the collector = 15 cm, rotation speed = 2000 rpm, temperature = 21°C, and humidity = 50%.

For 3D self-standing ES membranes, we adopted longer deposition times, 15 minutes for random fibers and 1 hour for aligned fibers, while other parameters were maintained unchanged. However, fibers were collected on an aluminium foil to allow their detachment. All samples were dried under a hood overnight and cut (1 cm x 1 cm) before use.

Polycaprolactone Films Spin Coating. The solution used for the fabrication of PCL (Mw 80,000 Da) films was prepared at a concentration of 5% w/v in chloroform. A small volume of the solution (125 μL) was spin-coated with an acceleration of 1500 rpm/s and a final speed of 3000 rpm for 50 seconds.



Polyvinyl alcohol solution preparation and electrospinning. Polyvinyl alcohol (PVA) electrospun fibers were prepared by dissolving Mowiol 18-88 (130 kDa) in deionized water at a concentration of 10% w/w. To ensure complete dissolution, the solution was maintained at 90°C and stirred overnight. Random fibers were obtained using a collector distance of 20 cm, voltage = 14 kV, and flow rate = 0.1 mL/h. For aligned fibers, the parameters were: rotation speed = 500 rpm, flow rate = 0.2 mL/h, collector distance = 20 cm, and voltage = 17 kV.

Fiber collection for 2D substrates followed the same method as for PCL. For self-standing membranes, the deposition time for both aligned and random samples was fixed at 1 hour and 45 minutes.

Polyvinyl Alcohol Fiber Crosslinking PVA samples require crosslinking to prevent fiber dissolution in water when used for cell culture. Crosslinking was performed by immersing the samples in a solution containing 0.2 M glutaraldehyde and 0.05 M hydrochloric acid in acetone for 1 hour and 30 minutes. The substrates were then washed three times with acetone, followed by deionized water, and left to dry overnight before use.

Scanning Electron Microscopy and Alignment Analysis All scaffolds were deposited on Silicon substrates and examined under a scanning electron microscope (SEM - Tescan Mira3) using secondary electron and an accelerating voltage of 5 kV to evaluate fiber morphology and diameter. Fiber alignment was analysed using ImageJ software by measuring the angle formed between the fibers and the vertical axis of each image. The fiber angles were normalized from 0° to 90°.

C2C12 cell culture C2C12 cells (ATCC) were cultured at 37 °C in a 5% CO₂ atmosphere, maintaining confluence below 70% to prevent damage. The cells were maintained through a maximum of 15 passages. The maintenance medium consisted of Dulbecco's Modified Eagle's Medium (DMEM) supplemented with 10% Fetal Bovine Serum and 2% glutamine.

Cells were seeded at a density of 197 cells/mm² for the 2D samples configuration and 394 cells/mm² for the 3D self-standing membranes. Before cell seeding, the scaffolds were sterilized under UV light for 1 h and 30 minutes and the samples were coated with a fibronectin solution (1:200 in Phosphate buffer without Ca²⁺ and Mg²⁺) to improve cell attachment. Upon reaching confluence, the medium was replaced with a starvation medium composed of DMEM and 2% glutamine. After four days, differentiation was induced using a medium containing DMEM, 2% glutamine, and 2% Horse Serum for 2D samples, while 3D samples received 10% Horse Serum²⁴ and insulin 1:1000 was added. Throughout the starvation and differentiation phases, the medium was refreshed every two days over a total duration of 12 days.

Confocal microscope images and fusion index analysis: Confocal microscope images have been taken by an inverted laser microscope, Nikon eclipse Ti2. Images were acquired using NIS-Elements (Nikon Imaging Software) with a 60x objective. Nuclei were stained with Hoechst (1:1000) and the cells membrane with cell mask deep red (1:1000) that were incubated for 5 minutes in PBS and then washed off. To evaluate the fusion index, a 20× objective was used and image analysis was performed using ImageJ.

Optical stimulation During the optical stimulation experiments, the cells were treated with Ziapin2 dissolved in Dimethylsulfoxide (DMSO). Ziapin2 was directly added to the cell's media reaching a final concentration of 25 µM for 2D samples and 50 µM in quasi-3D self-standing membranes. The multi-well plate was incubated for 10 minutes to allow internalization of the photochromic molecules before transferring the cells into an extracellular solution. The incubation time for self-standing membrane was 30 minutes. The extracellular solution contained NaCl (0.14 M), KCl (0.0054 M), MgCl₂ (0.0018 M), CaCl₂ (0.0018 M), glucose (0.011 M), and HEPES (0.01 M).

Optical stimulation and visualization were performed using a Nikon Eclipse Ti inverted microscope equipped with a 470 nm cyan LED source. A 20×/0.50 objective (Nikon) was used to observe myotube contractions in the samples. Cells were stimulated by pulse trains at three different frequencies: 0.5, 1, and 2 Hz. Light pulses lasted 200 ms for 0.5 and 1 Hz stimulation, while for 2



188 Hz, the pulse duration was reduced to 100 ms. In self-standing membranes only 1 Hz was used to
189 photostimulate the myotubes.

190 Video recordings of the stimulation experiments were acquired using PVcam software. Stimulation
191 began 20 seconds after video recording started and continued for several seconds beyond the end
192 of the protocol to determine whether contractions were externally triggered or resulted from intrinsic
193 biological activity. All experiments were conducted at 37 °C without CO₂ control.

194 **Electrical stimulation of ES membranes:** Electrical stimulation was performed by applying a 3 V
195 voltage at a frequency of 1 Hz, each pulse lasting 20 ms. The extracellular solution used during
196 stimulation followed a previously reported for the optical stimulation. All experiments were conducted
197 at room temperature without CO₂ regulation.

198 **Video analysis** Video analysis was performed using ImageJ and a MATLAB script. The script
199 included a visual recognition algorithm based on the Kanade–Lucas–Tomasi (KLT) method, which
200 tracks object movement across frames. The selected region of interest (ROI) was divided into
201 subregions, and coordinates for each subregion were extracted.

202 To quantify myotube contractions, the initial resting position in each video was set as the zero point.
203 The algorithm then calculated the average displacement of each point relative to this reference. The
204 analysis included measurements of the average displacement of the ROI, the contraction trajectory,
205 and the average contraction duration and frequency, following the methodology described by
206 Venturino et al.¹⁴

207 **Mechanical characterization** The ES membranes were evaluated using stress–strain
208 measurements to assess their mechanical properties. Before the measurement, the membrane
209 thickness was measured using a Hirox digital optical microscope (HRX-01) using the Z-stack
210 functionality. For the aligned substrates the force was applied in the preferential direction of
211 orientation of fibers through an Instron Mechanical Testing System (Instron, Norwood, MA, USA),
212 equipped with a load cell of 10 N. The tensile tests were performed with a displacement rate of 1
213 mm/min until fracture. Young's modulus was calculated from the slope of the initial 5% of the stress-
214 strain curve, considering the ratio of the applied load to the cross-sectional area.

215

216

217 Results and Discussion

218 Electrospinning process and fibers characterization

219 Electrospinning was chosen because it provides straightforward control over fiber alignment,
220 diameter, thickness and porosity, all properties known to influence myoblast alignment, fusion and
221 contractile maturation. In our protocol, alignment was achieved using a high-speed rotating collector,
222 whereas randomly oriented mats were collected on a static plate; increasing deposition time
223 produced self-standing membranes with the thickness required for quasi-3D cell culture (see
224 Methods for specific parameters). We selected PCL (C₆H₁₀O₂)_n and PVA (C₂H₄O)_n to sample
225 complementary material chemistries: PVA for its higher wettability and cell-friendly surface
226 properties, and PCL for its hydrophobicity and slower degradation. These design choices were made
227 *a priori* to produce bead-free, continuous fibers with micro-architectural features that promote contact
228 guidance and volumetric infiltration.

229 The four SEM images in Figure 1 are representative examples showing aligned vs. random fiber
230 organization and the absence of beads. For the SEM analysis, a small number of fibers were
231 collected on a silicon substrate to better evaluate their morphology, diameters, and fabrication
232 quality. In the case of PCL fibers, to prevent fiber detachment and improve adhesion to the substrate,
233 a PCL interlayer of 1057 ± 18 nm was spin-coated on glass. SEM analysis revealed smooth fibers,
234 free of beads or defects, as shown in Figure 1A-B. Slight differences in fibers diameter were
235 observed between randomly oriented and aligned fibers of the same material. The measurement



carried out on SEM micrographs showed in all cases a diameter of a few hundred nm more specifically: 250 ± 16 nm for PVA-aligned, 225 ± 13 nm for PVA-random, 312 ± 64 nm for PCL-aligned, and 260 ± 38 nm in the case of PCL-random. (Figure S1-2 Supplementary) The angle distribution of the fibers was extracted and normalized from 0° to 90° , and represented in polar plots, where the radial axis indicates the percentage of fibers aligned in each direction. The results reported in Figure 1 show, as expected, that electrospinning deposition on a fixed substrate leads to randomly oriented fibers (both PVA and PCL), as evidenced by the broad angles distribution and the standard deviation value: $28^\circ \pm 17^\circ$ for PVA and $41^\circ \pm 21^\circ$ for PCL samples. In contrast, the aligned samples show fibers oriented predominantly between $80^\circ \pm 4^\circ$ and $88^\circ \pm 1^\circ$ (for PVA and PCL, respectively).

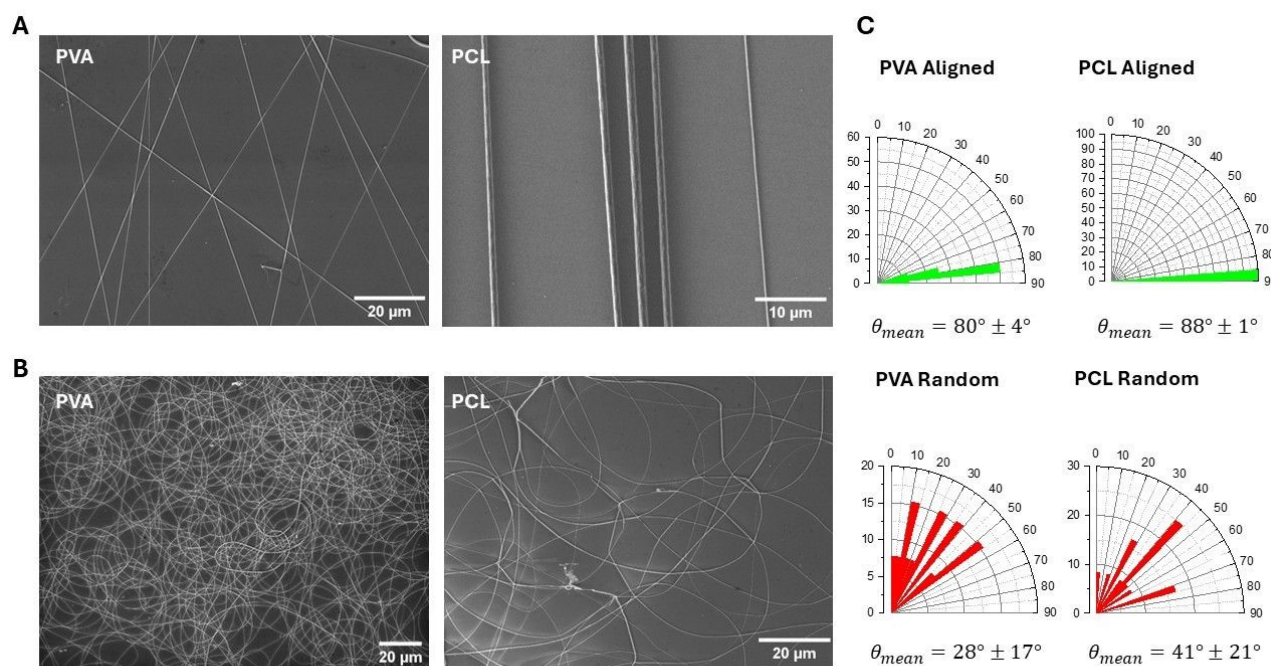


Figure 1. SEM images of A) Aligned PVA and PCL fibers, B) Random PVA and PCL fibers, C) Alignment degrees diagrams of each sample and mean angles.

C2C12 cells culture on 2D nanostructured substrates

Following morphological characterization, we evaluated 2D scaffolds made from both materials to identify the optimal substrate and fiber morphology for muscle-cell alignment and to determine which samples yielded the strongest myotube contractions. Between 7 and 12 days after seeding C2C12 myoblasts, myotube formation was evident in all scaffold types (Figure 2). Functional assays were then performed 12 days after the cells first reached confluence to ensure that the myotubes were sufficiently mature to contract.³⁹ Figure 2 presents optical microscopy images of differentiated skeletal muscle cells cultured on aligned and randomly oriented ES PVA and PCL fibers. In the aligned scaffolds, myotubes clearly follow the orientation of the underlying substrate (Figure 2A–B). Quantitative analysis, consistent with previous evaluations on neat ES networks, confirms the preferential alignment of myotubes in the oriented samples. Notably, myotubes exhibit an intrinsic tendency to align, as evidenced by a narrower angle distribution compared to that of the underlying fibers—even on randomly oriented scaffolds (Figure 2E). However, the influence of fiber orientation extends beyond geometric guidance, affecting both cell proliferation and functional maturation. Samples with randomly oriented fibers exhibit a reduced number of myotubes compared to those with aligned fibers (Figure 3 E-F). Only in the presence of aligned ES scaffolds, we observe the formation of a homogeneous cellular layer containing myotubes that display spontaneous contractile activity. To assess the extent of cellular organization on the different substrates, we quantified the



fusion index from confocal microscopy images, defined as the percentage of elongated, multinucleated cells containing more than two nuclei. Significant differences were observed among the substrates. The formation of elongated, multinucleated structures is commonly associated with myogenic progression in C2C12 cultures and is frequently used as a morphological indicator of myoblast fusion.⁴⁰ In addition, the observation of spontaneous contractions further supports the establishment of coordinated cellular assemblies. While fusion index and contractile activity are widely employed as functional and morphological readouts in engineered muscle systems, definitive confirmation of myogenic differentiation would require additional molecular analyses, such as immunostaining for lineage-specific markers (e.g., myosin heavy chain or actin)⁴¹ and gene expression evaluation by PCR. However, comprehensive molecular characterization was beyond the scope of the present study, which is primarily focused on the design, fabrication, and functional evaluation of light-responsive nanofiber scaffolds as materials platforms for guided cellular organization. Notably, the fusion index analysis revealed substantial substrate dependent differences.⁴² In the presence of aligned substrates, a higher fusion index was obtained compared to the random samples: aligned PVA showed the highest value of $62 \pm 8\%$, followed by aligned PCL with $48 \pm 12\%$. Randomly oriented PVA showed a fusion index of $30 \pm 3\%$, while randomly oriented PCL fusion index was $24 \pm 5\%$. All these values are represented in a box plot with the corresponding statistical analysis in Figure S4 of the supplementary materials and some representative confocal images for each sample in Figure S3. The pronounced increase in multinucleated cell formation observed on aligned substrates highlights the importance of nanostructured architectures that provide structural guidance through fiber anisotropy. Such alignment promotes parallel organization of myoblasts, facilitating end-to-end cellular arrangement and increasing the likelihood of membrane fusion events commonly associated with myotube development. The PVA promoted a higher fusion index compared to PCL. The superior performance of PVA may be attributed to its greater wettability and hydrophilicity compared to PCL.⁴³

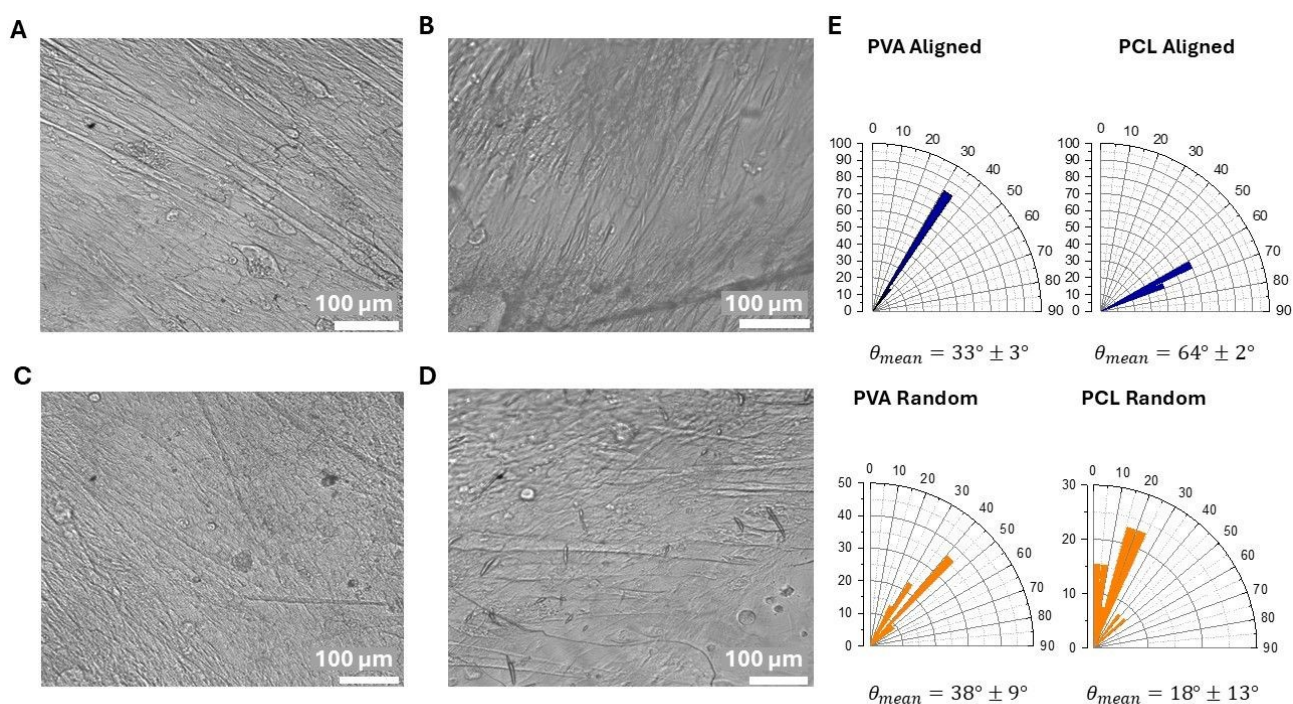


Figure 2. Optical microscope images of myotubes on A) PVA aligned substrates, B) PCL aligned substrates, C) PVA random substrates, D) PCL random fibers. E) Alignment degree diagrams of myotubes differentiated on each sample and mean angles. The dimensions of all the 2D substrates were 1cmx1cm.

Muscle cells opto-stimulation

298 Opto-stimulation and contraction analysis

View Article Online
DOI: 10.1039/D5TB02640G

299 Differentiated C2C12 cells on 2D substrates were incubated with the amphiphilic azobenzene
300 Ziapin2 to enable light-induced contractions. This molecule is designed to spontaneously partition
301 into the lipid membrane through non-covalent interactions and modulate membrane potential via its
302 *trans*→*cis* photoisomerization reaction. Briefly, upon partitioning, Ziapin2 tends to aggregate, leading
303 to membrane thinning, hence an associated increase in capacitance. Photoisomerization disrupts
304 these aggregates, restoring membrane thickness and producing a transient, reversible decrease in
305 membrane capacitance. As demonstrated by Moschetta et al.⁴⁴, Ziapin2 modulates strain-sensitive
306 ion channels, which play a key role in excitation-contraction coupling.⁴⁵ The strain-induced opening
307 of these channels causes transient potential hyperpolarization, followed by a rebound depolarization,
308 sufficient to trigger an action potential. Although such a behaviour has proven to be general, as it
309 has been observed in neurons, cardiomyocytes, skeletal muscle cells and bacteria^{46–49}, the key
310 novelty of this work is to provide a demonstration of Ziapin2-mediated optostimulation in 3D, tissue-
311 like, muscle constructs supported by nanostructured, stretchable scaffolds. This advance is not a
312 trivial extension of prior work: in moving to 3D, geometrically complex, nanostructured systems, the
313 effectiveness of Ziapin2 could not be taken for granted. Being a materials-driven paradigm, factors
314 such as molecular aggregation, and light scattering can hinder isomerization and critically affect the
315 optostimulation performances.

316 The cells were stimulated at 0.5, 1, and 2 Hz with 30-second light pulses trains with 200 ms pulse
317 duration. The pacing efficiency was evaluated by working out contraction frequency distributions.
318 These were extracted from videos recorded during photostimulation experiments using a 20x
319 objective, the frequency analysis was conducted by a MATLAB algorithm employing visual
320 recognition. The algorithm identifies and tracks myotube movement by selecting a region of interest
321 (ROI) and following its displacement across each video frames. This approach enables extraction of
322 the ROI position throughout the recording, allowing reconstruction of the myotube contraction
323 profile.²⁴ In PVA-aligned samples, under 0.5 Hz stimulation (Figure 3A) approximately 80% of the
324 myotubes precisely followed the light stimulus. However, in randomly oriented PVA fibers (Figure
325 3B), the percentage of myotubes contracting at 0.5 Hz dropped to 50%. In contrast, PCL samples
326 maintained a similar percentage of myotubes (~80%) able to perfectly follow the pacing in both
327 aligned and random fiber arrangements (Fig. 3 C-D). It is worth mentioning that the increases in the
328 stimulation frequency generally led to decreased myotube performance in both aligned and random
329 substrates for PVA (Figure S5 and S6 for PCL, Supplementary Materials). The number of contractile
330 areas (regions containing actively contracting myotubes) and the total number of contractile
331 myotubes can be extracted from the videos and correspond to the number of ROIs where such
332 activity is observed for each sample type. PVA-aligned scaffolds show the best performance, both
333 in terms of contractile area count and myotube number (Figure 3E–F). In contrast, PVA-random
334 scaffolds exhibit nearly half of these values. A similar, though less pronounced, trend is observed in
335 PCL scaffolds. The most pronounced differences were observed between PVA aligned and random
336 substrates, whereas the differences between PCL and PVA did not reach statistical significance.
337 These results may support the hypothesis that pre-aligning cells prior to differentiation enhances
338 myotube maturation, as further evidenced by the fusion index analysis. In Figure S7 of the
339 Supporting Information, the mean contraction frequency analysis is also reported for the control
340 samples, in which myoblasts were differentiated on a planar 2D surface without any nanostructure.
341 These controls show a lower percentage of myotubes able to precisely follow the light stimulation
342 frequency at each applied stimulation frequency.

343



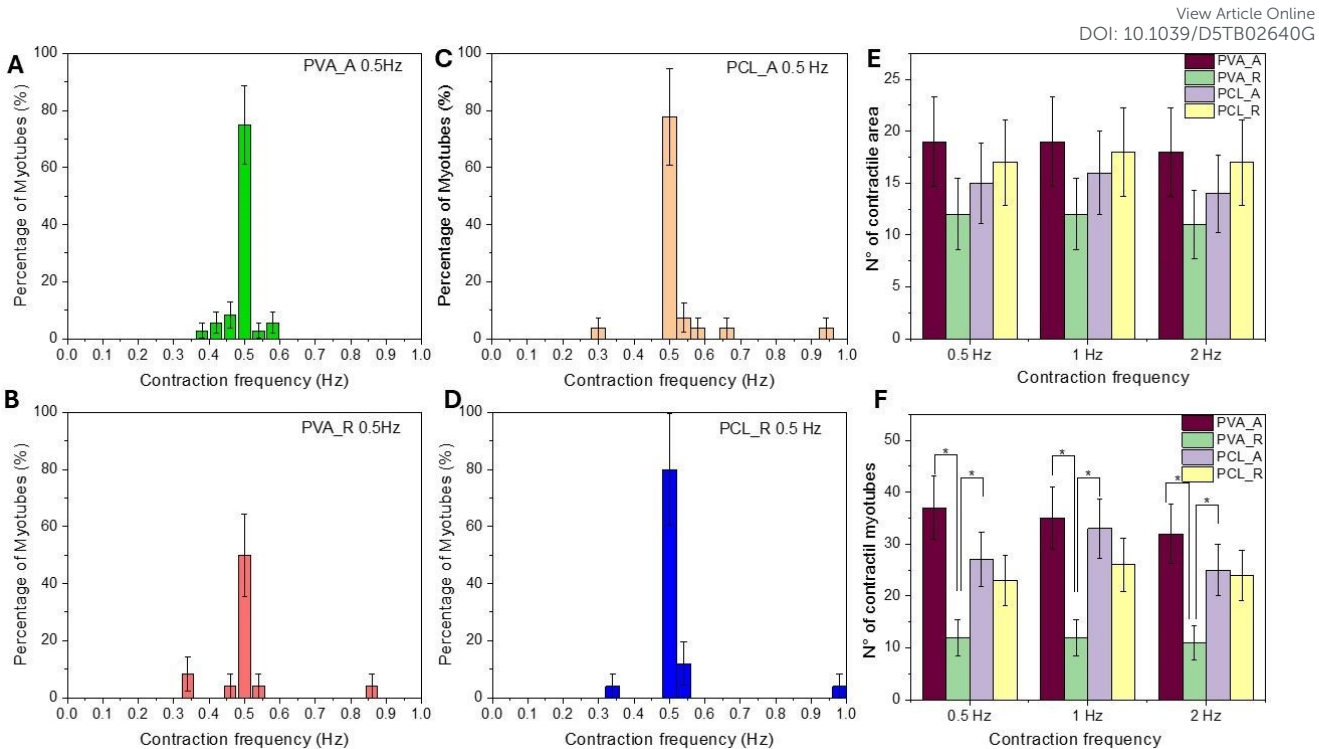


Figure 3. Histogram represents the mean contraction frequency of myotubes photostimulated at 0.5 Hz in A) aligned PVA 2D sample, B) random PVA 2D sample, C) aligned PCL 2D sample, D) random PCL 2D sample. Bin sizes are based on the standard error of the frequency, whereas the error on the bar is $\sqrt{N}\%$. E) Histograms of the number of contractile areas in each type of sample at different light frequency stimulations. F) Number of contractile myotubes in different types of fiber orientations at different light frequency stimulations. Six samples were analyzed for each scaffold in the analysis reported in E and F (the error bar is calculated as $\sqrt{N}$). All the samples were illuminated with a blue LED (470 nm) at a power density of 42 mW/mm². T-student was performed as statistical analysis (*p<0.05).

Mechanical characterization of self-standing membrane in air

Aiming at increasing the volume of contractile tissue, as it happens in real muscular constructs, we then realized self-standing membranes by increasing the deposition time and keeping parameters and materials unchanged with respect to the 2D substrates deposition. The electrospun (ES) membranes were characterized by SEM to evaluate the presence of defects and the organization of the fibers (Figure S9, Supplementary Information). To evaluate the suitability of the ES membranes for C2C12 differentiation and their compatibility with cell contraction, the mechanical properties of the self-standing membranes in air were assessed by determining their Young's moduli. The thickness of the ES membranes used in the tensile test experiments was measured with a profilometer on three samples and found to be approximately $43 \pm 15 \mu\text{m}$ for PCL aligned, $56 \pm 8 \mu\text{m}$ for PCL random, $35 \pm 3 \mu\text{m}$ for PVA aligned, and $53 \pm 8 \mu\text{m}$ for PVA random (Figure S10 Supplementary Materials). Figure 4A compares Young's modulus (E) for both materials in aligned and random configurations obtained by fitting the elastic region of the stress-strain curves shown in Figure S11 (Supplementary Materials). The PVA random sample exhibits a Young's modulus that is almost one order of magnitude higher than the others, probably because the highly interconnected and entangled fiber network offers greater resistance to the applied force. All nanofibers' membranes are well suited for tissue engineering applications because their E values are in the 10-90 MPa range.⁵⁰ This turns out to be a distinct advantage of ES fibers, as in thin films, of both PVA and PCL, the Young's modulus is in the GPa range.^{51,52} Electrospinning also confers inherent porosity to the membrane, reducing material density for a given volume, thus increasing flexibility, and introducing defined surface topography.^{53,54} Based on our comparative analysis, we therefore conclude that a combination of interrelated material properties, such as surface wettability, microstructure/topography, and the local mechanical environment, mechanical properties and

myotube density, fusion index, and light-responsive contractile performance, aligned PVA was the optimal material for fabricating tissue-like quasi-3D scaffolds. This choice was further supported by the absence of organic solvents during the fabrication process and the potential for future scaffold functionalization due to the presence of hydroxyl groups.

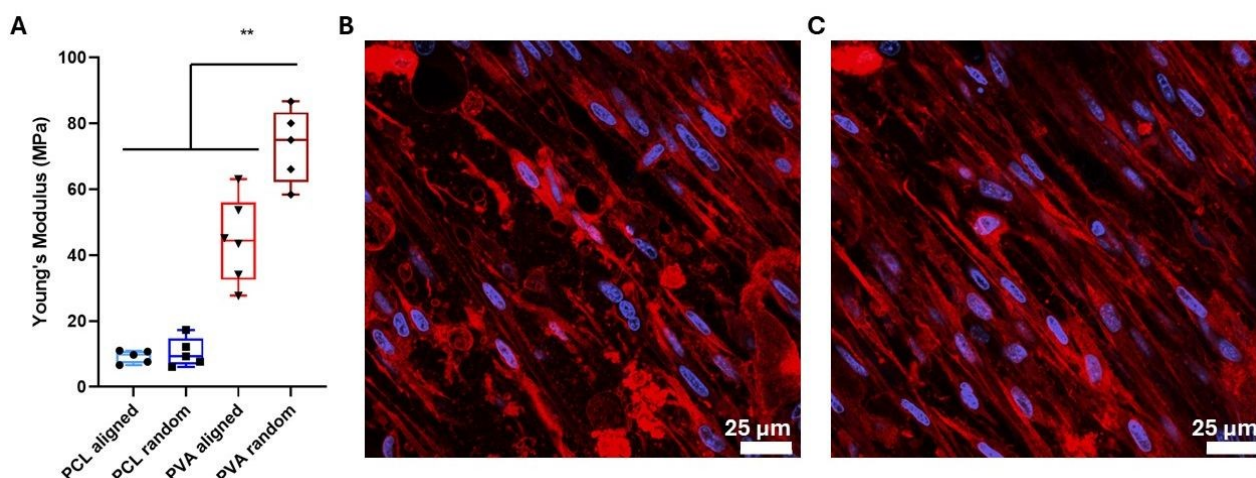


Figure 4. A) Comparison between Young's modulus of wet aligned and random fibers. B) Image of the bottom focal plane from confocal z-stack, in blue myotubes nuclei, in red cells membrane. C) Upper focal plane. In aligned samples the tensile strength was applied in the preferential fiber direction (anisotropic axis) and the random were treated as isotropic under the same test configuration.

C2C12 Proliferation and Photoinduced Contractile Biomechanics of quasi- 3D PVA Scaffolds

Twelve days after seeding, we acquired confocal images to assess tissue-like cell distribution and proliferation. C2C12 nuclei were stained with Hoechst and cell membranes with CellMask Deep Red. In Figure 4B–C, two representative cross-sections of the self-standing PVA membrane reveal the presence of cell nuclei distributed throughout the thickness of the material. This distribution demonstrates that cells did not remain confined to the surface but were able to migrate and populate deeper layers of the scaffold. Such infiltration indicates that the membrane architecture and porosity allow cells stacking and a quasi-3D tissue like organization. In the SI (Figure S8) we reported also the maximum and the minimum intensity projection of the construct and a 3D image of the Z- stacked slices (Video 1).

To evaluate the contractile capabilities of this construct, we first applied conventional electrical stimulation before proceeding to the new photostimulation paradigm using Ziapin2. To observe the contraction, we employed a 20x objective, and the cell-seeded scaffolds were stimulated at 1 Hz (20 ms pulses, 3V). Our PVA-based quasi-3D cell-seeded scaffold exhibited clear macroscopic contractions induced by a train of electrical stimuli at 1 Hz (Supplementary video 2). Having observed that standard electrostimulation drives a clear contractile behaviour, we then proceed to optical stimulation on samples sensitized with Ziapin2, noting well-defined and precise photoinduced contractions (Supplementary video 3).

Once the ability to contract under exogenous stimuli was demonstrated qualitatively, we performed a quantitative analysis of the contraction dynamics and mechanical actuation. Specifically, we calculated a photoinduced ES membrane displacement (ΔL_0) of 4 μm and, knowing the elastic modulus (E) of the membrane and its initial length (L_0) we could estimate the contraction-induced stress using the formula $\sigma = E \Delta L / L_0$ (with $\Delta L / L_0$ representing the deformation ε) and then obtained the force generated by the muscle tissue using the equation $F = \sigma A_{ef}$, where A_{ef} is the effective area. In the area evaluation, we considered the porosity of the ES membranes starting from value reported in literature of $\phi = 0.6$ ⁵⁵ and the area was calculated as $A_{ef} = A_0(1 - \phi)$ where A_0 is the area without voids. We used the effective Young's modulus of the sample measured after 12 days of incubation in the cell medium (DMEM), which turns out to be 8.26 MPa, a value that is sensibly



Open Access Article. Published on 16 February 2026. Downloaded on 2/16/2026 6:19:04 PM.
This article is licensed under a Creative Commons Attribution 3.0 Unported Licence.


413 lower than the 42 MPa measured in dry conditions (Figure S12, Supplementary materials). In terms
414 of generated force optical stimulation permits to reach a value of 460 μN and a stress of 3.3 kPa. All
415 values used for calculation are summarized in Table 1.
416 These values significantly overperform typical stress values for 2D films, in the order of 0.5 kPa.⁵⁶
417 We attribute the effectiveness of our approach to the presence of a quasi-3D cellular organization
418 and relatively high degree of alignment. In particular, literature reports that 3D constructs of C2C12
419 cells generate specific contractile stresses ranging from approximately 1 to 50 kPa, depending on
420 the construct organization, substrate materials, degree of differentiation, and stimulation
421 protocol.^{36,38} It is also interesting to note that photoinduced contractions fall within the same order of
422 magnitude as those produced by conventional electrical pacing ($\Delta L \approx 7.7 \mu\text{m}$; force $\approx 890 \mu\text{N}$; stress
423 $\approx 6 \text{ kPa}$ see Supplementary Materials). Although direct comparison is challenging, given the different
424 modes of stimulation and energy inputs, we evaluated the photo- and electrical-induced
425 biomechanics both at maximum light intensity and the strongest electrical stimulus compatible with
426 cell viability.²⁴ Under these conditions, photostimulation emerges as a minimally invasive yet highly
427 effective method for driving muscle contraction.
428 As a final note, using the average active tension generated by a single myotube ($F_{sm} = 0.88 \mu\text{N}$),⁵⁴
429 we estimate that producing 460 μN of force requires roughly 523 contractile myotubes. Given our
430 electrospun membrane dimensions, the total volume is about 3.5 mm^3 ; accounting for porosity, the
431 available volume for cell growth and differentiation ($\phi \approx 0.641$) reduces roughly 2 mm^3 . With an
432 average myotube measuring 20 μm in diameter ⁵⁷ and 300 μm in length,⁵⁸ each occupies
433 approximately $1 \times 10^{-4} \text{ mm}^3$, so all 523 active myotubes together fill about 0.05 mm^3 , which is the
434 2.5 percent of the scaffold's available space. This occupancy highlights substantial room for
435 increasing cell density and alignment, and thus contractile output, through optimized seeding
436 strategies, scaffold design, or extended culture protocols.
437

Sample	Thickness	Length	Width	ΔL_o	E	A_o	A_{ef}	σ_o
PVA aligned	35 $\pm$ 3 μm	10 mm	10 mm	3.5 $\pm$ 0.4 μm	8.26 $\pm$ 3 MPa	0.35 mm^2	0.14 mm^2	2.9 $\pm$ 0.3 kPa

438 Table 1. Summary of the ES PVA Aligned self-standing membrane average parameters used for the force calculation. The
439 displacement is obtained upon optical stimulation at 470 nm (42 mW/mm^2) and with a frequency of 1 Hz. Here we reported
440 the best performances for both, while other values are reported in Figure S13 in Supplementary materials

441 **Conclusions**

442 In this work, we demonstrate that electrospun PVA nanofiber membranes provide a quasi-3D
443 microenvironment that supports C2C12 alignment and enables macroscopic force generation. The
444 aligned fiber architecture provides contact guidance through its anisotropic structure, promoting
445 parallel cellular organization and increasing the formation of elongated, multinucleated structures,
446 as quantified by orientation analysis and fusion index measurements. While definitive confirmation
447 of myogenic differentiation would require comprehensive molecular characterization (e.g.,
448 immunostaining for structural proteins and gene expression analysis), the present study was
449 primarily focused on materials design and functional scaffold performance. Within this framework,
450 the observation of organized, multinucleated cellular assemblies capable of spontaneous and light-
451 induced contractions supports the development of a biohybrid photoactuation platform.
452 Implementation of the membranes as free-standing constructs enables volumetric cell organization,
453 as demonstrated by confocal z-stack imaging showing nuclei distributed throughout the membrane
454 thickness, consistent with a three-dimensional cellular arrangement within the porous fibrous
455 network. In parallel, in situ mechanical testing established that hydrated membranes exhibit an
456 elastic modulus of approximately 8 MPa, providing mechanically robust support for handling and
457 actuation under physiological conditions.

Functionally, optical stimulation of Ziapin2-infiltrated membranes under visible light produces reproducible construct contractions (displacements $\sim 4\ \mu\text{m}$), corresponding to estimated forces up to $\sim 460\ \mu\text{N}$ and stresses up to $\sim 3.3\ \text{kPa}$ based on measured displacement and scaffold mechanical parameters. Although only a fraction of the available scaffold volume appears occupied by contractile cellular assemblies, suggesting opportunities for further optimization of cell density and maturation, these results establish free-standing electrospun nanofiber membranes as a versatile platform for light-addressable muscle-like constructs with potential applications in soft bioactuation, drug screening, in vitro modelling, and regenerative medicine.

Author Contributions

Conceptualization, G.S., G.L.; methodology, G.S., I.V., F.M. and V.V.; synthesis, P.M., M.R. and C.B.; validation, G.S.; formal analysis, G.S., G.M.P. and G.L.; investigation, G.S., A.B., L.V. and L.A.; data curation, G.S., G.M.P. and G.L.; writing – original draft, G.S.; writing – review & editing, G.S., F.M., V.V., A.B., L.V., G.M.P. and G.L.; visualization, G.S.; supervision, G.M.P., C.B. and G.L.; project administration, G.S. and G.L.; funding acquisition, G.L.

Conflicts of Interest

The authors declare that they have no competing interests.

Data Availability

All resources used in this work are included in the published article and its supplemental information files. The data contained in this paper can be found here [10.5281/zenodo.15727910](https://doi.org/10.5281/zenodo.15727910).

Acknowledgments

VV and GL acknowledge Fondo Italiano per la Scienza project (ID FIS00001244). G.M.P. thanks the European Union for financial support (ERC, EOS, 101115925). Work supported by #NEXTGENERATIONEU (NGEU) and funded by the Ministry of University and Research (MUR), National Recovery and Resilience Plan (NRRP), project MNESYS (PE0000006) – A Multiscale integrated approach to the study of the nervous system in health and disease (DN. 1553 11.10.2022).

References

1. Pacilio, S. *et al.* Electrospun Poly(L-lactide-co- ϵ -caprolactone) Scaffold Potentiates C2C12 Myoblast Bioactivity and Acts as a Stimulus for Cell Commitment in Skeletal Muscle Myogenesis. *Bioengineering* **10**, 239 (2023).
2. Kozan, N. G., Joshi, M., Sicherer, S. T. & Grasman, J. M. Porous biomaterial scaffolds for skeletal muscle tissue engineering. *Front. Bioeng. Biotechnol.* **11**, 1245897 (2023).
3. Lo, C.-Y. *et al.* Highly stretchable self-sensing actuator based on conductive photothermally-responsive hydrogel. *Mater. Today* **50**, 35–43 (2021).
4. Florindi, C., Simoncini, G., Lanzani, G. & Lodola, F. Shining light in a heartbeat: Controlling cardiac bioelectricity with membrane-targeted photoswitches. *Appl. Phys. Lett.* **126**, 230501 (2025).
5. Chen, C., Hou, W. & He, X. NeuroMuscles: Pioneering materials open a new path to artificial skeletal muscles. *Matter* **8**, (2025).
6. Li, M., Pal, A., Aghakhani, A., Pena-Francesch, A. & Sitti, M. Soft actuators for real-world applications. *Nat. Rev. Mater.* **7**, 235–249 (2022).



- 504 7. Ershad, F. *et al.* Bioprinted optoelectronically active cardiac tissues. *Sci. Adv.* **11**, eadt7210 (2025). Article Online
DOI: 10.1039/D5TB02640G
- 505
- 506 8. Almonacid Suarez, A. M., Zhou, Q., van Rijn, P. & Harmsen, M. C. Directional topography
- 507 gradients drive optimum alignment and differentiation of human myoblasts. *J. Tissue Eng.*
- 508 *Regen. Med.* **13**, 2234–2245 (2019).
- 509 9. Ku, S. H., Lee, S. H. & Park, C. B. Synergic effects of nanofiber alignment and electroactivity
- 510 on myoblast differentiation. *Biomaterials* **33**, 6098–6104 (2012).
- 511 10. Bettadapur, A. *et al.* Prolonged Culture of Aligned Skeletal Myotubes on Micromolded Gelatin
- 512 Hydrogels. *Sci. Rep.* **6**, 28855 (2016).
- 513 11. Mao, W., Lee, S., Kim, S.-R., Kim, K.-N. & Yoo, H. S. Electrospun nanohybrid hydrogels for
- 514 enhanced differentiation of myoblasts. *J. Ind. Eng. Chem.* **80**, 838–845 (2019).
- 515 12. Pacilio, S. *et al.* Electrospun Poly(L-lactide-co- ϵ -caprolactone) Scaffold Potentiates C2C12
- 516 Myoblast Bioactivity and Acts as a Stimulus for Cell Commitment in Skeletal Muscle
- 517 Myogenesis. *Bioengineering* **10**, 239 (2023).
- 518 13. Ma, Z., Kotaki, M., Inai, R. & Ramakrishna, S. Potential of Nanofiber Matrix as Tissue-
- 519 Engineering Scaffolds. *Tissue Eng.* **11**, 101–109 (2005).
- 520 14. Balint, R., Cassidy, N. J. & Cartmell, S. H. Electrical Stimulation: A Novel Tool for Tissue
- 521 Engineering. *Tissue Eng. Part B Rev.* **19**, 48–57 (2013).
- 522 15. Vurro, V., Venturino, I. & Lanzani, G. A perspective on the use of light as a driving element for
- 523 bio-hybrid actuation. (2022).
- 524 16. Aloisio, L. *et al.* Insight on the Intracellular Supramolecular Assembly of DTTO: A Peculiar
- 525 Example of Cell-Driven Polymorphism. *Adv. Mater.* **35**, 2302756 (2023).
- 526 17. Asano, T., Ishizua, T. & Yawo, H. Optically controlled contraction of photosensitive skeletal
- 527 muscle cells. *Biotechnol. Bioeng.* **109**, 199–204 (2012).
- 528 18. Bruegmann, T. *et al.* Optogenetic control of contractile function in skeletal muscle. *Nat.*
- 529 *Commun.* **6**, 7153 (2015).
- 530 19. Raman, R. *et al.* Optogenetic skeletal muscle-powered adaptive biological machines. *Proc.*
- 531 *Natl. Acad. Sci.* **113**, 3497–3502 (2016).
- 532 20. A Polymer Blend Substrate for Skeletal Muscle Cells Alignment and Photostimulation - Vurro -
- 533 2021 - Advanced Photonics Research - Wiley Online Library.
- 534 <https://advanced.onlinelibrary.wiley.com/doi/full/10.1002/adpr.202000103>.
- 535 21. Lodola, F., Vurro, V., Crasto, S., Di Pasquale, E. & Lanzani, G. Optical Pacing of Human-
- 536 Induced Pluripotent Stem Cell-Derived Cardiomyocytes Mediated by a Conjugated Polymer
- 537 Interface. *Adv. Healthc. Mater.* **8**, e1900198 (2019).
- 538 22. Savchenko, A. *et al.* Graphene biointerfaces for optical stimulation of cells. *Sci. Adv.* **4**,
- 539 eaat0351 (2018).
- 540 23. Ganji, E., Chan, C. S., Ward, C. W. & Killian, M. L. Optogenetic activation of muscle
- 541 contraction in vivo. *Connect. Tissue Res.* **62**, 15–23 (2021).
- 542 24. Venturino, I. *et al.* Skeletal muscle cells opto-stimulation by intramembrane molecular
- 543 transducers. *Commun. Biol.* **6**, 1148 (2023).
- 544 25. Rizzi, R. *et al.* Tissue engineering for skeletal muscle regeneration. *Muscles Ligaments*
- 545 *Tendons J.* **2**, 230–234 (2012).
- 546 26. Wang, J. *et al.* Engineered skeletal muscles for disease modeling and drug discovery.
- 547 *Biomaterials* **221**, 119416 (2019).
- 548 27. Wang, J., Wang, Y., Kim, Y., Yu, T. & Bashir, R. Multi-actuator light-controlled biological
- 549 robots. *APL Bioeng.* **6**, 036103 (2022).
- 550 28. Teixeira, M. A., Amorim, M. T. P. & Felgueiras, H. P. Poly(Vinyl Alcohol)-Based Nanofibrous
- 551 Electrospun Scaffolds for Tissue Engineering Applications. *Polymers* **12**, 7 (2020).



29. Janmohammadi, M. & Nourbakhsh, M. S. Electrospun polycaprolactone scaffolds for tissue engineering: a review. *Int. J. Polym. Mater. Polym. Biomater.* **68**, 527–539 (2019). DOI: 10.1039/D5TB02640G
30. Molnar, K. *et al.* Biocompatibility study of poly(vinyl alcohol)-based electrospun scaffold for hernia repair. *Express Polym. Lett.* **12**, 676–687 (2018).
31. Zhang, Y. Z., Venugopal, J., Huang, Z.-M., Lim, C. T. & Ramakrishna, S. Characterization of the Surface Biocompatibility of the Electrospun PCL-Collagen Nanofibers Using Fibroblasts. *Biomacromolecules* **6**, 2583–2589 (2005).
32. Veliça, P. & Bunce, C. M. A quick, simple and unbiased method to quantify C2C12 myogenic differentiation. *Muscle Nerve* **44**, 366–370 (2011).
33. Vurro, V. *et al.* Molecular Design of Amphiphilic Plasma Membrane-Targeted Azobenzenes for Nongenetic Optical Stimulation. *Front. Mater.* **7**, 631567 (2021).
34. Paternò, G. M. *et al.* Membrane Environment Enables Ultrafast Isomerization of Amphiphilic Azobenzene. *Adv. Sci.* **7**, 1903241 (2020).
35. Vurro, V., Magni, A., Aloisio, L. & Lanzani, G. Photostimulation mechanism of an amphiphilic azobenzene. *Il Nuovo Cimento C* **46**, 1–4 (2023).
36. Vesga-Castro, C., Aldazabal, J., Vallejo-Illarramendi, A. & Paredes, J. Contractile force assessment methods for in vitro skeletal muscle tissues. *eLife* **11**, e77204 (2022).
37. Guimarães, C. F., Gasperini, L., Marques, A. P. & Reis, R. L. The stiffness of living tissues and its implications for tissue engineering. *Nat. Rev. Mater.* **5**, 351–370 (2020). ¹
38. Kah, D. *et al.* Contractility of cardiac and skeletal muscle tissue increases with environmental stiffness. 2024.02.23.581737 Preprint at <https://doi.org/10.1101/2024.02.23.581737> (2024).
39. Bajaj, P. *et al.* Patterning the differentiation of C2C12 skeletal myoblasts. *Integr. Biol.* **3**, 897–909 (2011).
40. Zocchi, M., Béchet, D., Mazur, A., Maier, J. A. & Castiglioni, S. Magnesium Influences Membrane Fusion during Myogenesis by Modulating Oxidative Stress in C2C12 Myoblasts. *Nutrients* **13**, 1049 (2021).
41. Chakraborty, M., Sivan, A., Biswas, A. & Sinha, B. Early tension regulation coupled to surface myomerger is necessary for the primary fusion of C2C12 myoblasts. *Front. Physiol.* **13**, (2022).
42. Martin, N. R. W. *et al.* Factors affecting the structure and maturation of human tissue engineered skeletal muscle. *Biomaterials* **34**, 5759–5765 (2013).
43. Calero-Castro, F. J. *et al.* Mechanical Stimulation and Aligned Poly(ϵ -caprolactone)–Gelatin Electrospun Scaffolds Promote Skeletal Muscle Regeneration. *ACS Appl. Bio Mater.* **7**, 6430–6440 (2024).
44. Moschetta, M. *et al.* Modulation of Mechanosensitive Potassium Channels by a Membrane-targeted Nongenetic Photoswitch. *J. Phys. Chem. B* **127**, 8869–8878 (2023).
45. McBride, T. A., Stockert, B. W., Gorin, F. A. & Carlsen, R. C. Stretch-activated ion channels contribute to membrane depolarization after eccentric contractions. *J. Appl. Physiol.* **88**, 91–101 (2000).
46. de Souza-Guerreiro, T. C. *et al.* Membrane Targeted Azobenzene Drives Optical Modulation of Bacterial Membrane Potential. *Adv. Sci.* **10**, 2205007 (2023).
47. DiFrancesco, M. L. *et al.* Neuronal firing modulation by a membrane-targeted photoswitch. *Nat. Nanotechnol.* **15**, 296–306 (2020).
48. Vurro, V. *et al.* Light-triggered cardiac microphysiological model. *APL Bioeng.* **7**, 026108 (2023).
49. Vurro, V. *et al.* Optical modulation of excitation-contraction coupling in human-induced pluripotent stem cell-derived cardiomyocytes. *iScience* **26**, 106121 (2023).
50. Riboldi, S. A., Sampaolesi, M., Neuenschwander, P., Cossu, G. & Mantero, S. Electrospun degradable polyesterurethane membranes: potential scaffolds for skeletal muscle tissue engineering. *Biomaterials* **26**, 4606–4615 (2005).



51. Chen, W., Tao, X., Xue, P. & Cheng, X. Enhanced mechanical properties and morphological characterizations of poly(vinyl alcohol)–carbon nanotube composite films. *Appl. Surf. Sci.* **252**, 1404–1409 (2005).
52. Jones, D. S., Djokic, J., McCoy, C. P. & Gorman, S. P. Poly(ϵ -caprolactone) and poly(ϵ -caprolactone)-polyvinylpyrrolidone-iodine blends as ureteral biomaterials: characterisation of mechanical and surface properties, degradation and resistance to encrustation in vitro. *Biomaterials* **23**, 4449–4458 (2002).
53. Diwan, T., Abudi, Z. N., Al-Furaiji, M. H. & Nijmeijer, A. A Competitive Study Using Electrospinning and Phase Inversion to Prepare Polymeric Membranes for Oil Removal. *Membranes* **13**, 474 (2023).
54. Yan, B., Zhang, Y., Li, Z., Zhou, P. & Mao, Y. Electrospun nanofibrous membrane for biomedical application. *SN Appl. Sci.* **4**, 172 (2022).
55. Mustafa, F. E. & Lee, B.-K. Improved Mechanical Stability and Regulated Gentamicin-Release of Polyvinyl Alcohol/Chitosan Nanofiber Membranes via Heat Treatment. *J. Biomed. Mater. Res. A* **113**, e37905 (2025).
56. Fujita, H., Shimizu, K. & Nagamori, E. Novel method for measuring active tension generation by C2C12 myotube using UV-crosslinked collagen film. *Biotechnol. Bioeng.* **106**, 482–489 (2010).
57. Girgis, C. M., Clifton-Bligh, R. J., Mokbel, N., Cheng, K. & Gunton, J. E. Vitamin D Signaling Regulates Proliferation, Differentiation, and Myotube Size in C2C12 Skeletal Muscle Cells. *Endocrinology* **155**, 347–357 (2014).
58. Ostrovidov, S. *et al.* Three-dimensional co-culture of C2C12/PC12 cells improves skeletal muscle tissue formation and function. *J. Tissue Eng. Regen. Med.* **11**, 582–595 (2017).



DATA AVAILABILITY STATEMENT

View Article Online
DOI: 10.1039/D5TB02640G

All resources used in this work are included in the published article and its supplemental information files. The data contained in this paper can be found here [10.5281/zenodo.15727910](https://doi.org/10.5281/zenodo.15727910).

